

VDM® Crofer 22 APU

Crofer® 22 APU* is a high-temperature ferritic stainless steel especially developed for application in solid oxide fuel cells (SOFC).

At temperatures up to 900 °C (1652 °F) a chromium-manganese oxide layer is formed on the surface of Crofer® 22 APU which is thermodynamically very stable and possesses high electrical conductivity. The low coefficient of thermal expansion is matched to that of ceramics typically used for high-temperature fuel cells in the range from room temperature to 900 °C (1652 °F).

Crofer® 22 APU is characterized by:

- excellent corrosion resistance at high temperatures in anode gas and cathode gas
- low rate of chromium vaporization
- ease of working and processing
- low coefficient of thermal expansion
- good electrical conductivity of the oxide layer

Designations and standards

Country	Material designation	Specification		
		Chemical composition	Sheet & Plate	Strip
National standards				
D	W.-Nr. 1.4760			
DIN EN	X1CrTiLa22			
USA	UNS S44535			
ASTM		A 240	A 240	

Table 1 - Designations and standards.

Chemical composition

	Cr	Fe	C	Mn	Si	Cu	Al	S	P	Ti	La
min.	20.0	bal.		0.30						0.03	0.04
max.	24.0		0.03	0.80	0.50	0.50	0.50	0.020	0.050	0.20	0.20

Table 2 – Chemical composition (wt.-%).

* ThyssenKrupp VDM GmbH produces Crofer® 22 APU (APU = Auxiliary Power Unit) under licence from Forschungszentrum Jülich.

Physical properties

Density	7.7 g/cm ³	0.278 lb/in. ³
Melting range	1510 °C (Solidus) - 1530 °C (Liquidus)	2750 °F (Solidus) - 2786 °F (Liquidus)

Temperature (T)		Specific heat		Thermal conductivity		Electrical resistivity (ρ)		Modulus of elasticity		Coefficient of thermal expansion between 20 °C/68°F and T	
°C	°F	$\frac{J}{kg \cdot K}$	$\frac{Btu}{lb \cdot ^\circ F}$	$\frac{W}{m \cdot K}$	$\frac{Btu \cdot in.}{ft^2 \cdot h \cdot ^\circ F}$	$\mu\Omega \cdot cm$	$\frac{\Omega \cdot circ \text{ mil}}{ft}$	$\frac{kN}{mm^2}$	10 ³ ksi	$\frac{10^{-6}}{K}$	$\frac{10^{-6}}{^\circ F}$
25	77	470	0.112	26	180	55	330	220	31.9		
200	392	520	0.124	23	160	70	421	210	30.5	10.3	5.7
400	752	610	0.146	23	160	90	541	195	28.3	10.8	6.0
500	932							183	26.5	11.2	6.2
600	1112					105	632			11.4	6.3
700	1292									11.6	6.4
800	1472	660	0.158	24	166	115	692			11.9	6.6
900	1652									12.3	6.8
1000	1832	650	0.155	27	187	120	722			12.7	7.1

Table 3 - Typical physical properties at room and elevated temperatures.

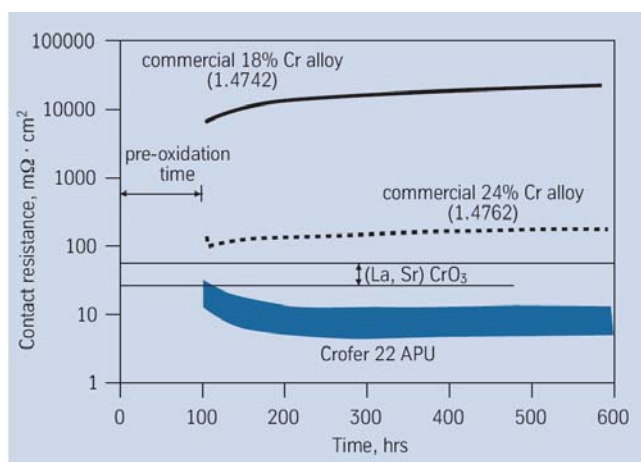


Fig. 1 – Contact resistance of various materials used for SOFC in air at 800 °C. (After Quadackers et al., Forschungszentrum Jülich)

Figure 1 shows the contact resistance of Crofer® 22 APU as a function of time while exposed to air at 800 °C. The contact resistance of Crofer® 22 APU is an order of magnitude lower than traditional ferritic alloy 446 (1.4762) type stainless steels. This is because Crofer® 22 APU forms a protective scale that exhibits good electrical conductivity and no SiO₂ sublayer which shows poor electrical conductivity.

Mechanical properties

Thickness	0.2 % Yield strength $R_{p0.2}$		Tensile strength R_m		Elongation A_{50} %	Hardness HRB (For information only)
	MPa	ksi	MPa	ksi		
0.25 – 0.38 mm (0.010 – 0.015")	≥ 250	≥ 36.6	≥ 350	≥ 50.8	≥ 20	70 - 90
≥ 0.38 mm (0.015")	≥ 250	≥ 36.6	≥ 350	≥ 50.8	≥ 25	70 - 90

Table 4 - Minimum mechanical properties in the soft-annealed condition for all product forms at room temperature.

Product	0.2 % Yield strength $R_{p0.2}$		Tensile strength R_m		Elongation A_{50} %
	MPa	ksi	MPa	ksi	
Sheet & Plate	270	39.1	370	53.7	30
Strip	320	46.4	450	65.3	30
Wire	350	50.8	500	72.5	15

Table 5 - Typical mechanical properties for different product forms at room temperature.

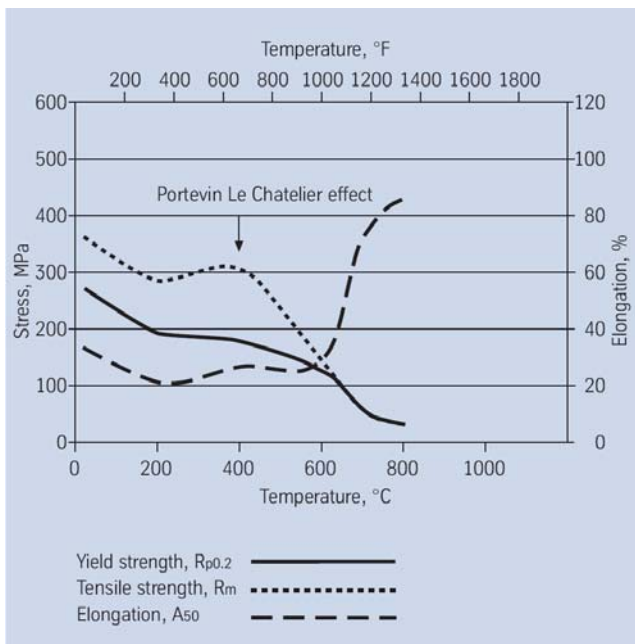


Fig. 2 - Typical short-time mechanical properties of soft-annealed Crofer[®] 22 APU, 22 mm plate, as a function of temperature.

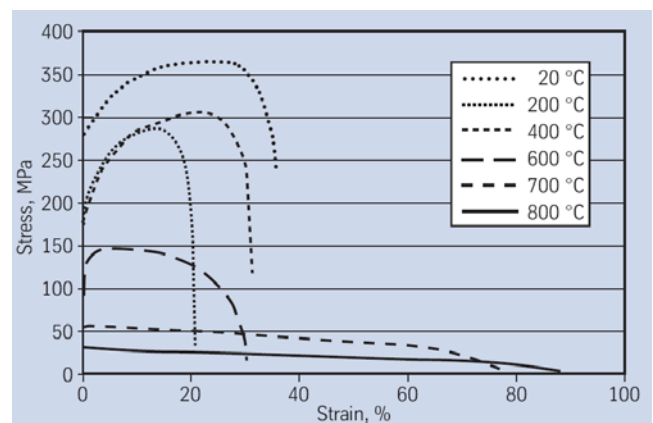


Fig. 3 - Stress-Strain curves for Crofer[®] 22 APU at various temperatures.

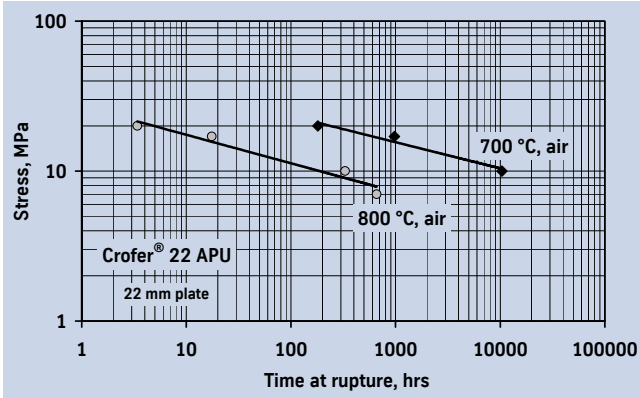


Fig. 4 - Typical creep-rupture strength of soft-annealed Crofer® 22 APU from current production. (After B. Kuhn et al., Forschungszentrum Jülich)

Metallurgical structure

Crofer® 22 APU has a body-centered-cubic structure.

Corrosion resistance

Crofer® 22 APU shows excellent corrosion resistance in atmospheres relevant to SOFC applications up to 900 °C. The oxide layer of Crofer 22® APU consists of a fine grained inner scale which is predominantly Cr₂O₃ and a columnar (Mn, Cr)₃O₄ spinel outer oxide layer. This outer layer reduces chromia evaporation very effectively as shown in Figure 6.

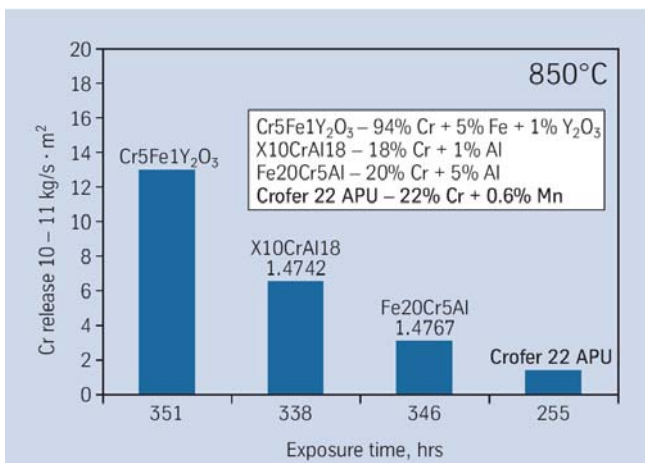


Fig. 6 - Chromium release of several materials at 850 °C in humidified synthetic air with 2% H₂O (2 x 10³ Pa). (After Hilpert, Gindorf et al., Forschungszentrum Jülich)

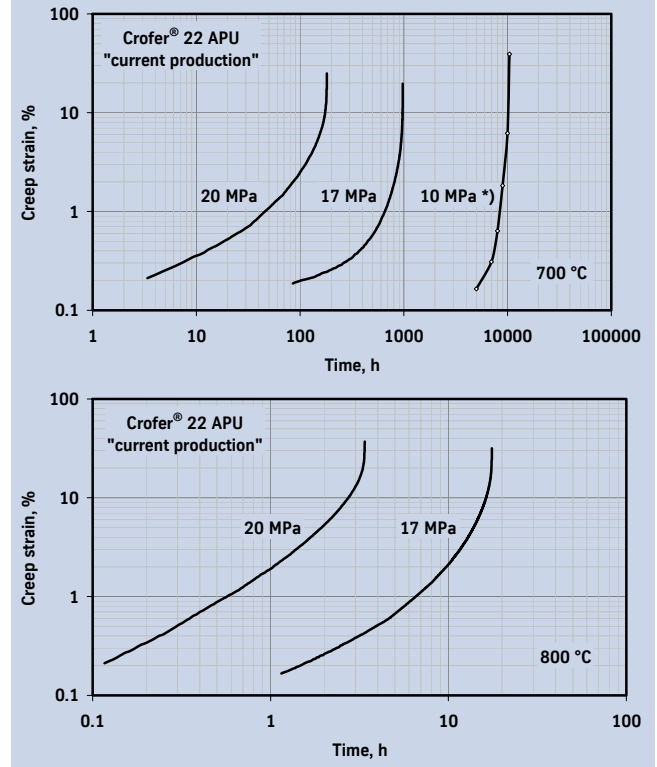


Fig. 5 - Typical creep strain - time curves of soft annealed Crofer® 22 APU in air. All curves are from a continuous elongation measurement at the sample except *, which is from discontinuous elongation measurement (After B. Kuhn et al., Forschungszentrum Jülich)

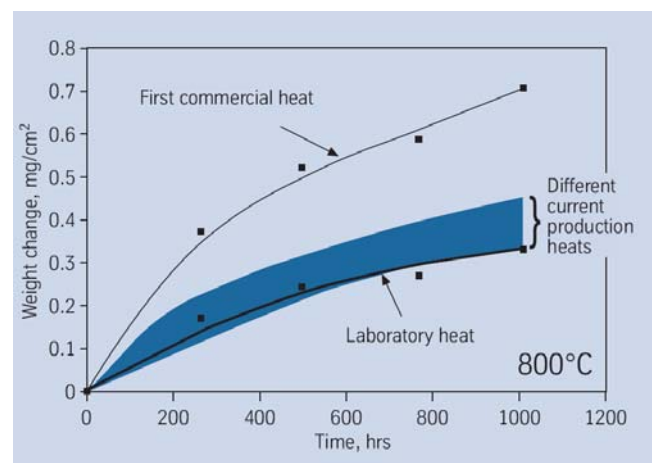


Fig. 7 - Mass change during discontinuous oxidation tests (250 h cycles) of a laboratory and commercially produced Crofer® 22 APU heats in air at 800 °C as a function of time. (After Quadackers et al., Forschungszentrum Jülich)

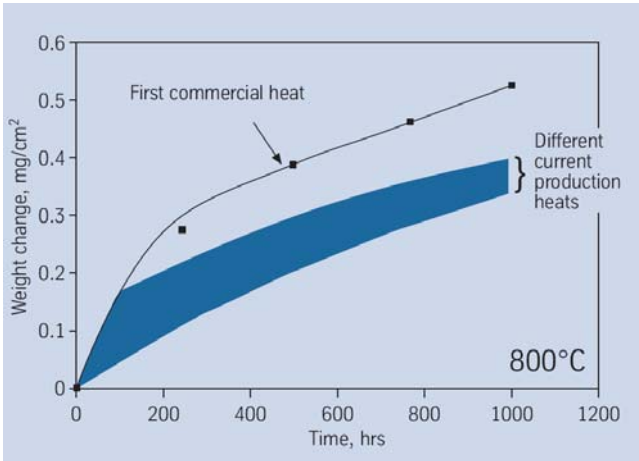


Fig. 8 - Mass change during discontinuous oxidation tests (100 h cycles except for the first commercial heat, where 250 h cycles were used) of commercially produced Crofer[®] 22 APU heats in simulated anode gas (Ar + 4% H₂ + 2% H₂O) at 800 °C as a function of time. (After Quadakkers et al., Forschungszentrum Jülich)

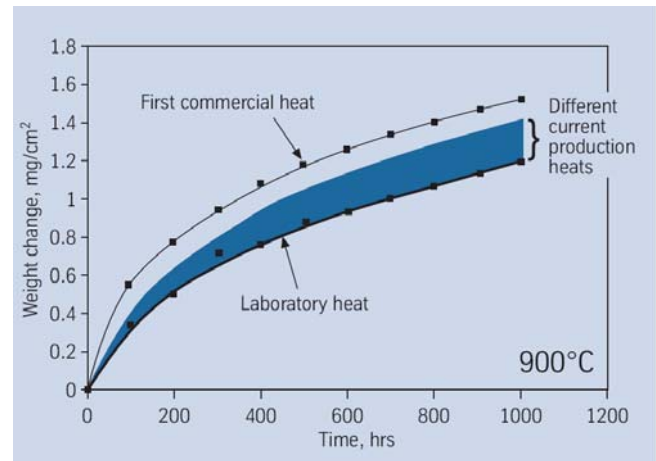


Fig. 9 - Mass change during discontinuous oxidation tests (100 h cycles) of a laboratory and commercially produced Crofer[®] 22 APU heats in simulated anode gas (Ar + 4% H₂ + 20% H₂O) at 900 °C as a function of time. (After Quadakkers et al., Forschungszentrum Jülich)

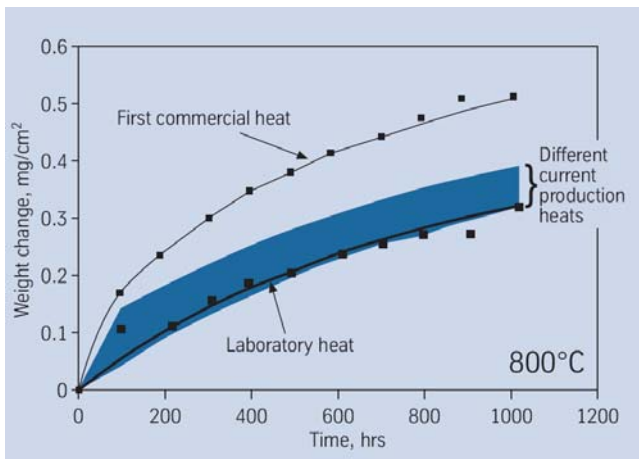


Fig. 10 - Mass change during discontinuous oxidation tests (100 h cycles) of a laboratory and commercially produced Crofer[®] 22 APU heats in simulated carbon containing anode gas (Ar + 4% H₂ + 10% CO + 2% H₂O) at 800 °C as a function of time. (After Quadakkers et al., Forschungszentrum Jülich)

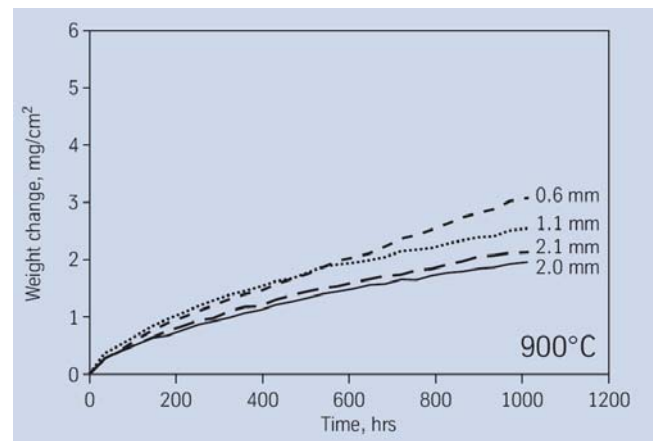


Fig. 11 - Mass change during cyclic oxidation tests in air (cycles of 2 h heating and 15 min. cooling) of samples of varying thickness from a Crofer[®] 22 APU production heat restricted in residual elements. (After Quadakkers et al., Forschungszentrum Jülich)

Figures 7 to 10 show the corrosion resistance of Crofer[®] 22 APU in atmospheres relevant to SOFC applications at 800 °C and 900 °C respectively. Current production restricts the residual element content in comparison to the first commercial heat. This results in a vast improvement of the oxidation behavior as clearly shown in Figures 7 to 10 for several commercial heats (sample thickness ranging from 1.5 to 2 mm). For comparison the results of the laboratory heat melted with high-purity prematerials prior to the first commercial heat are also included in Figures 7, 9 and 10.

Apart from the restriction in residual elements Figure 11 clearly shows that the thickness of sheet material also has a significant effect on the oxidation resistance of Crofer[®] 22 APU.

Applications

Crofer[®] 22 APU is used for interconnector plates to separate individual plates in solid oxide fuel cells (SOFC).

Fabrication and heat treatment

Crofer[®] 22 APU can readily be hot and cold worked and machined.

Heat treatment

Production pieces must be clean and free from all kinds of contaminants before and during any heating operation.

Crofer[®] 22 APU may become embrittled if heated in the presence of contaminants such as sulfur, phosphorus, lead and other low-melting-point metals. Sources of such contaminants include marking and temperature-indicating paints and crayons, lubricating grease, fluids and fuels.

Fuels must be as low in sulfur as possible. Natural gas should contain less than 0.1 wt.-% sulfur. Liquid fuels with a sulfur content not exceeding 0.5 wt.-% are suitable.

Due to their close control of temperature and lack of contamination, thermal treatments in electric furnaces under vacuum or in an inert gas atmosphere are to be preferred. Treatments in an air atmosphere and, alternatively, in gas-fired furnaces are acceptable though, if contaminants are kept at low levels so that a neutral or slightly oxidizing furnace atmosphere is attained. A furnace atmosphere fluctuating between oxidizing and reducing conditions must be avoided as well as direct flame impingement on the metal.

After cold forming a recrystallization heat treatment is required. Figure 12 shows the effect on grain size of 50 % cold formed Crofer[®] 22 APU of such a thermal treatment for various temperatures and time-at-temperature intervals.

Descaling and pickling

Oxides of Crofer[®] 22 APU and discoloration adjacent to welds are more adherent than on standard stainless steels. Grinding with very fine abrasive belts or discs is recommended. Care should be taken to prevent tarnishing.

Before pickling in a nitric/hydrofluoric acid mixture, the surface oxide layer must be broken up by abrasive blasting or grinding or by pretreatment in a fused salt bath. Particular attention should be paid to the pickling time and temperature.

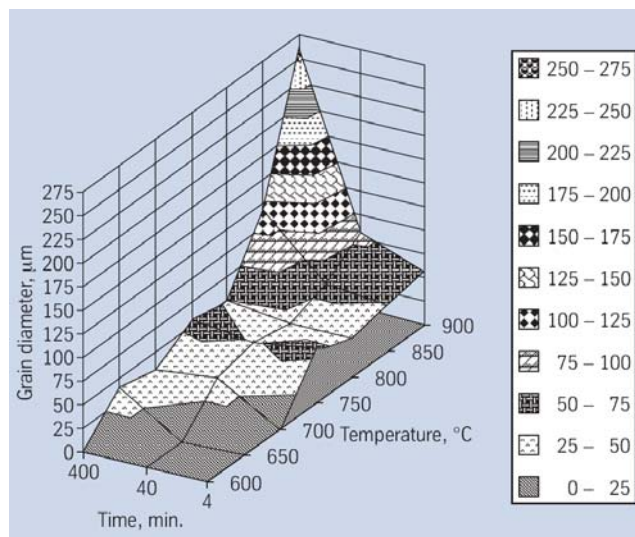


Fig. 12 - Recrystallization diagram of Crofer[®] 22 APU after 50% cold deformation.

Welding

When welding high alloyed stainless steels or nickel alloys, the following instructions should be adhered to:

Workplace

The workplace should be in a separate location, well away from areas where carbon steel fabrication takes place. Maximum cleanliness and avoidance of draughts are paramount.

Auxiliaries, clothing

Clean fine leather gloves and clean working clothes should be used.

Tools and machines

Tools used for nickel alloys and stainless steels must not be used for other materials. Brushes should be made of stainless materials.

Fabricating and working machinery such as shears, presses or rollers should be fitted with means (felt, cardboard, plastic sheeting) of avoiding contamination of the metal with ferrous particles, which can be pressed into the surface and thus lead to corrosion.

Cleaning

Cleaning of the base metal in the weld area (both sides) and of the filler metal (e. g., welding rod) should be carried out with ACETONE.

Trichlorethylene (TRI), perchlorethylene (PER) and carbon tetrachloride (TETRA) must not be used as they are detrimental to health.

Edge preparation

This should preferably be done by mechanical means by turning, milling or planing; abrasive water jet or plasma cutting is also suitable. However, in the latter case the cut edge (the face to be welded) must be finished off cleanly. Careful grinding without overheating is permitted.

Included angle

The different physical characteristics of nickel alloys and special stainless steels compared with carbon steel generally manifest themselves in a lower thermal conductivity and a higher rate of thermal expansion.

This should be allowed for by means of, among other things, wider root gaps or openings (2 mm ≤ 0.5 mm), while larger included angles (60 – 70°), as shown in Figure 13, should be used for individual butt joints owing to the viscous nature of the molten weld metal and to counteract the pronounced shrinkage tendency.

Striking the arc

The arc should only be struck in the weld area, i. e., on the faces to be welded or on a run-out piece. Striking marks lead to corrosion.

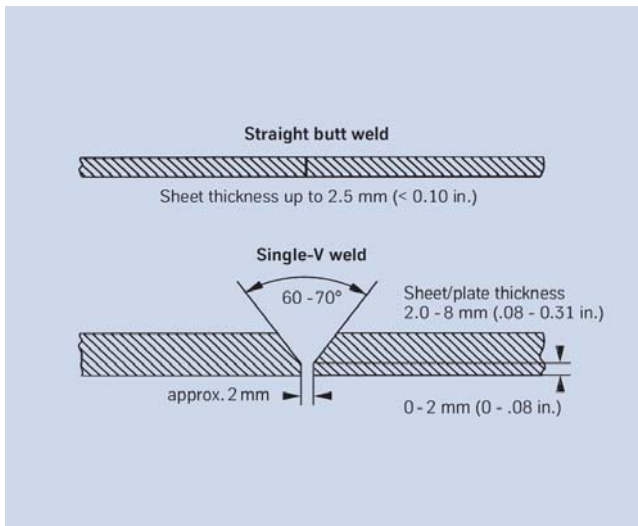


Fig. 13 – Edge preparation for welding of Crofer[®] 22 APU.

Welding process

Crofer[®] 22 APU in thin thicknesses (≤ 1.5 mm/0.06 in.) can be joined to itself by GTAW (TIG) and plasma arc welding without the use of filler metal. It can also be joined by spot welding or roll-seam welding.

For welding, Crofer[®] 22 APU should be in the soft-annealed condition and be free from scale, grease and markings. When welding the root, care should be taken to achieve best-quality root backing (argon 99.99), so that the weld is free from oxides after welding the root. Any heat tint should be removed preferably by brushing with a stainless steel wire brush while the weld metal is still hot.

Filler metal

For the GTAW (TIG) welding process filler metal with the same composition as the base metal is recommended.

Welding parameters and influences (heat input)

Care should be taken that the work is performed with a deliberately chosen, low heat input as indicated in Tables 6 and 7 by way of example. Use of the stringer bead technique should be aimed at. Interpass temperature should be kept below 120 °C (250 °F).

The welding parameters should be monitored as a matter of principle.

The heat input Q may be calculated as follows:

$$Q = \frac{U \times I \times 60}{v \times 1000} \text{ (kJ/cm)}$$

U = arc voltage, volts
 I = welding current, amps
 v = welding speed, cm/min.

Consultation with ThyssenKrupp VDM's Welding Laboratory is recommended.

Postweld treatment

(brushing, pickling and thermal treatments)

Brushing with a stainless steel wire brush immediately after welding, i.e., while the metal is still hot, generally results in removal of heat tint and produces the desired surface condition without additional pickling.

Pickling, if required or prescribed, however, would generally be the last operation performed on the weldment. Also refer to the information under 'Descaling and pickling'.

Neither pre- nor postweld thermal treatments are normally required.

Sheet/ plate thick- ness	Welding- process	Filler metal		Welding parameter				Welding speed	Shielding gas Type & rate	Plasma gas Type & rate
		diameter	speed	Root pass		Intermediate and final passes				
		mm	m/min.	I A	U V	I A	U V			
3.0	Manual GTAW	2.0		80	10	110 – 120	11	approx. 15	Ar 4.6 8 – 10	
5.0	Manual GTAW	2.0 – 2.4		90 – 100	11	130 – 140	13	14 – 16	Ar 4.6 8 – 10	
3.0	Autom. GTAW	1.2	approx. 1.2	Manual GTAW		160	11	25	Ar 4.6 12 – 14	
5.0	Autom. GTAW	1.2	approx. 1.4	Manual GTAW		200 – 220	approx. 13	25	Ar 4.6 12 – 14	
3.0	Hot wire GTAW	1.0				180	11	80	Ar 4.6 12 – 14	
5.0	Hot wire GTAW	1.2		Manual GTAW		220	13	40	Ar 4.6 12 – 14	
4.0	Plasma arc	1.2	approx. 1.0	approx. 180	25			30	Ar 4.6 30	Ar 4.6 3.0
6.0	Plasma arc	1.2	approx. 1.0	200 - 220	26			26	Ar 4.6 30	Ar 4.6 3.5

In all gas-shielded welding operations, adequate back shielding using Ar 4.6 must be ensured. Figures are for guidance only and are intended to facilitate setting of the welding machines.

Table 6 – Welding parameters (guide values).

Welding process	Heat input per unit length kJ/cm
GTAW, manual, fully mechanised	max. 8
Hot wire GTAW	max. 6
Plasma arc	max. 10

Table 7 – Heat input per unit length (guide values).

Technical Publications

The following publications concerning Crofer® 22 APU may be obtained from ThyssenKrupp VDM GmbH or can be downloaded from www.thyssenkruppvdm.com.

R. Hojda, W. Heimann, W.J. Quadackers:
Production - capable materials concept for high-temperature fuel cells; ThyssenKrupp techforum, July 2003.

R. Hojda:
Großserientaugliches Werkstoffkonzept für Brennstoffzellen; SCOPE - Das moderne Industriemagazin, April 2004.

R. Hojda, W. J. Quadackers:
Improved product Crofer® 22 APU; Reprint RP 1/05 from ThyssenKrupp techforum, July 2005.

R. Hojda, L. Paul:
UNS S44535 alloy development for interconnect applications in solid oxide fuel cells; CORROSION 2006, Paper No. 06479, NACE International, Houston, 2006.

H. Hattendorf, L. Paul, L. Niewolak, V. Shemet, P. Ennis, W. Quadackers
Practical Aspects of Using Crofer® 22 APU for Interconnects in Solid Oxide Fuel Cell;
2007 Fuel Cell Seminar; San Antonio, Texas, October 2007.

Further publications concerning Crofer® 22 APU and solid oxide fuel cells (SOFC) may be obtained from the Forschungszentrum Jülich, Dept. IEF-2, 52425 Jülich, Germany.

Availability

Crofer® 22 APU is available as sheet & plate, strip and wire.

Sheet & Plate

(for cut-to-length availability, refer to strip)

Conditions:

hot or cold rolled (hr, cr), soft-annealed and pickled

Thickness mm	hr/cr	Width ¹⁾ mm	Length ¹⁾ mm
1.10 - < 1.50	cr	2000	8000
1.50 - < 3.00	cr	2500	8000
3.00 - < 7.50	cr/hr	2500	8000
7.50 - ≤ 25.00	hr	2500	8000

¹⁾ Other sizes subject to special enquiry

Thickness inches	hr/cr	Width ¹⁾ inches	Length ¹⁾ inches
0.043 - < 0.060	cr	80	320
0.060 - < 0.120	cr	100	320
0.120 - < 0.300	cr/hr	100	320
0.300 - ≤ 1.000	hr	100	320

¹⁾ Other sizes subject to special enquiry

Strip¹⁾

Conditions

cold rolled, solution annealed and pickled or bright annealed²⁾

Thickness mm	Width ³⁾ mm	Coil I.D. mm
0.02 - ≤ 0.10	4 - 200 ⁴⁾	300 400
> 0.10 - ≤ 0.25	4 - < 720 ⁴⁾	300 400 500
> 0.25 - ≤ 0.6	6 - < 750	400 500 600
> 0.60 - ≤ 1.0	8 - < 750	400 500 600
> 1.0 - ≤ 2.0	15 - < 750	400 500 600
> 2.0 - ≤ 3.0 ²⁾ - ≤ 3.5 ²⁾	25 - < 750	400 500 600

¹⁾ Cut-to-length available in lengths from 250 to 4000 mm

²⁾ Maximum thickness: bright annealed - 3 mm
cold rolled only - 3.5 mm

³⁾ Wider widths subject to special enquiry

⁴⁾ Wider widths up to 730 mm subject to special enquiry

Thickness inches	Width ³⁾ inches	Coil I.D. inches
0.0008 - ≤ 0.004	0.16 - 8 ⁴⁾	12 16
> 0.004 - ≤ 0.010	0.16 - 14 ⁴⁾	12 16 20
> 0.010 - ≤ 0.024	0.24 - 30	16 20 24
> 0.024 - ≤ 0.040	0.32 - 30	16 20 24
> 0.040 - ≤ 0.080	0.60 - 30	16 20 24
> 0.080 - ≤ 0.120 ²⁾ - ≤ 0.140 ²⁾	1.00 - 30	16 20 24

¹⁾ Cut-to-length available in lengths from 10 to 158 in.

²⁾ Maximum thickness: bright annealed - 0.120 in.
cold rolled only - 0.140 in.

³⁾ Wider widths subject to special enquiry

⁴⁾ Wider widths up to 29 in. subject to special enquiry

Wire

Conditions:

drawn, bright, thermally treated;

drawn, bright, thermally treated, redrawn 1/4 hard to hard;
shaved or ground.

Dimensions:

drawn wire: 0.16 – 10 mm (0.0063 – 0.40 in.) diameter,
on spools, in coils and payoff packs; also available on
spiders and special spools.

The information contained in this data sheet is based on results of research and development work and data listed in applicable specifications and standards available and in effect at the time of printing. It does not provide any guarantee of particular characteristics or fit. ThyssenKrupp VDM reserves the right to make changes without notice. The data sheet has been compiled to the best knowledge of ThyssenKrupp VDM and is given without any liability on the part of ThyssenKrupp VDM. ThyssenKrupp VDM is only liable according to the terms of the sales contract, and in particular to the General Conditions of Sales in case of any delivery from ThyssenKrupp VDM. As updates of data sheets are not automatically sent out when issued ThyssenKrupp VDM recommends to request the latest edition of required data sheets either by phone +49 2392 55-2588, by fax +49 2392 55-2596, or by email under vdm@thyssenkrupp.com. Current issues of brochures and data sheets are also available on the Internet under www.thyssenkruppvdm.com

May 2010 Edition.

Imprint

Date of publication

May 2010

Publisher

VDM Metals GmbH
Plettenberger Straße 2
58791 Werdohl
Germany

Disclaimer

All information contained in this data sheet are based on the results of research and development work carried out by VDM Metals GmbH, and the data contained in the specifications and standards listed available at the time of printing. The information does not represent a guarantee of specific properties. VDM Metals reserves the right to change information without notice. All information contained in this data sheet is compiled to the best of our knowledge and is provided without liability. Deliveries and services are subject exclusively to the relevant contractual conditions and the General Terms and Conditions issued by VDM Metals GmbH. Use of the most up-to-date version of this data sheet is the responsibility of the customer.

VDM Metals GmbH
Plettenberger Straße 2
58791 Werdohl
Germany

Phone +49 (0) 2392 55-0
Fax +49 (0) 2392 55-2217

vdm@vdm-metals.com
www.vdm-metals.com